

UNCLASSIFIED

AD NUMBER	
AD339501	
CLASSIFICATION CHANGES	
TO:	UNCLASSIFIED
FROM:	SECRET
LIMITATION CHANGES	
TO: Approved for public release; distribution is unlimited.	
FROM: Distribution authorized to U.S. Gov't. agencies and their contractors; Administrative/Operational Use; 07 OCT 1960. Other requests shall be referred to Defense Threat Reduction Agency, 8725 John J. Kingman Road, Fort Belvoir, VA 22060-6201.	
AUTHORITY	
HQ DNA ltr dtd 28 Feb 1980 and DSWA/OPSSI ltr dtd 8 May 1998; HQ DNA ltr dtd 28 Feb 1980 and DSWA/OPSSI ltr dtd 8 May 1998	

THIS PAGE IS UNCLASSIFIED

THIS REPORT HAS BEEN DELIMITED
AND CLEARED FOR PUBLIC RELEASE
UNDER DOD DIRECTIVE 5200.20 AND
NO RESTRICTIONS ARE IMPOSED UPON
ITS USE AND DISCLOSURE.

DISTRIBUTION STATEMENT A

APPROVED FOR PUBLIC RELEASE,
DISTRIBUTION UNLIMITED.

UNCLASSIFIED

AD

339501

CLASSIFICATION CHANGED

TO: UNCLASSIFIED

FROM: SECRET

AUTHORITY:

DNAL 28 Feb 80

UNCLASSIFIED

~~RESTRICTED DATA~~

AD 339501L

DEFENSE DOCUMENTATION CENTER

FOR

SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION, ALEXANDRIA, VIRGINIA




~~RESTRICTED DATA~~
~~SECRET~~

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

NOTICE:

THIS DOCUMENT CONTAINS INFORMATION
AFFECTING THE NATIONAL DEFENSE OF
THE UNITED STATES WITHIN THE MEAN-
ING OF THE ESPIONAGE LAWS, TITLE 18,
U.S.C., SECTIONS 793 and 794. THE
TRANSMISSION OR THE REVELATION OF
ITS CONTENTS IN ANY MANNER TO AN
UNAUTHORIZED PERSON IS PROHIBITED
BY LAW.

DISCLAIMER NOTICE

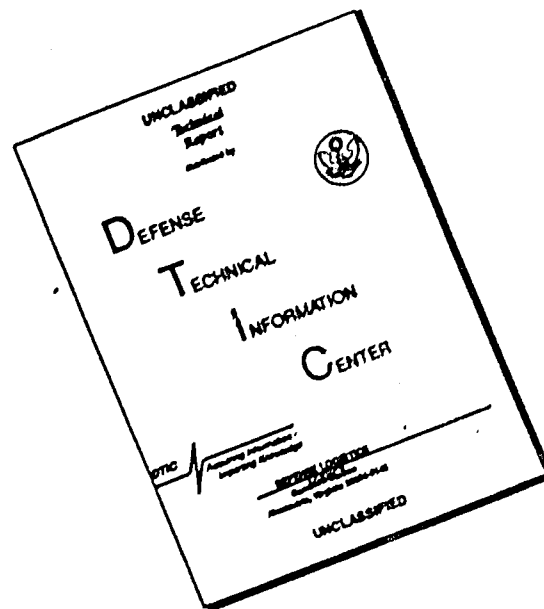

THIS DOCUMENT IS BEST QUALITY AVAILABLE. THE COPY FURNISHED TO DTIC CONTAINED A SIGNIFICANT NUMBER OF PAGES WHICH DO NOT REPRODUCE LEGIBLY.

AIR FORCE
BALLISTIC MISSILE DIVISION
TECHNICAL LIBRARY

Document No.

Copy No.

RESTRICTED DATA

SECRET

WT-1489

This document consists of 22 pages.

No. 83 of 165 copies, Series A

OPERATION

PLUMBBOB



NEVADA TEST SITE
MAY-OCTOBER 1957

Project 6.2a

**EFFECT of NUCLEAR RADIATION on
SEMICONDUCTOR DEVICES (U)**

Issuance date: October 7, 1960

HEADQUARTERS FIELD COMMAND
DEFENSE ATOMIC SUPPORT AGENCY
SANDIA BASE, ALBUQUERQUE, NEW MEXICO

RESTRICTED DATA

This document contains restricted data as defined in the Atomic Energy Act of 1954. Its transmittal or the disclosure of its contents in any manner to an unauthorized person is prohibited.

SECRET

EXCLUDED FROM AUTOMATIC
DOWNGRADING. DOD DIR 5206.10
DOES NOT APPLY

339501L



Inquiries relative to this report may be made to

Chief, Defense Atomic Support Agency
Washington 25, D. C.

When no longer required, this document may be
destroyed in accordance with applicable security
regulations.

DO NOT RETURN THIS DOCUMENT

SECRET
RESTRICTED DATA

WT-1489

OPERATION PLUMBBOB—PROJECT 6.2a

*EFFECT of NUCLEAR RADIATION on
SEMICONDUCTOR DEVICES, (U)*

P. H. Haas, Project Officer
J. M. Shaul
W. V. Behrens.

Diamond Ordnance Fuze Laboratories
Washington 25, D. C.

of the National
of the
and
Secret
limited

RESTRICTED DATA

This document contains restricted data as defined in the Atomic Energy Act of 1954. Its transmittal or the disclosure of its contents in any manner to an unauthorized person is prohibited.

3
SECRET

SECRET

FOREWORD

This report presents the final results of one of the 46 projects comprising the military-effects program of Operation Plumbbob, which included 24 test detonations at the Nevada Test Site in 1957.

For overall Plumbbob military-effects information, the reader is referred to the "Summary Report of the Director, DOD Test Group (Programs 1-9)," ITR-1445, which includes: (1) a description of each detonation, including yield, zero-point location and environment, type of device, ambient atmospheric conditions, etc.; (2) a discussion of project results; (3) a summary of the objectives and results of each project; and (4) a listing of project reports for the military-effects program.

RESTRICTED DATA

SECRET

ABSTRACT

A total of 350 transistors and semiconductor diodes, including germanium and silicon types, were exposed to nuclear detonations. Some of the transistors were operational during exposure as oscillators, amplifiers, and trigger circuits. Radiation levels varied from 10^{11} to 4×10^{11} NVT (n/cm^2) integrated neutron flux, accompanied by gamma radiation between 0.1 and 100,000 r.

The transistors showed a decrease in common-emitter current gain (β_{DC}) and an increase in collector-diode reverse leakage current (I_{CO}). The higher-frequency transistors were less affected by neutron fluxes than were the audio units, and the surface-barrier types were virtually undamaged by the maximum fluxes obtained. Semiconductor diodes showed an increase in forward resistance and a decrease in back resistance, with point-contact types showing much less change than the junction types.

Transistors and diodes in operating equipment suffered permanent damage comparable to those passively exposed. Degradation of performance of this equipment was almost entirely attributable to changes in the semiconductor parameters.

The results obtained are in reasonable agreement with data obtained from pile-type reactors, indicating that total integrated neutron flux is of primary significance, rather than rate of exposure.

CONTENTS

FOREWORD - - - - -	4
ABSTRACT - - - - -	5
EFFECT OF NUCLEAR RADIATION ON SEMICONDUCTOR DEVICES	
Objectives - - - - -	9
Background - - - - -	9
Theory - - - - -	9
Procedure - - - - -	10
Results - - - - -	11
Discussion - - - - -	13
Conclusions - - - - -	18
Recommendations - - - - -	19
REFERENCES - - - - -	20
FIGURES	
1 Containers for semiconductor devices for special tests - - - - -	10
2 Circuit diagrams of transistorized devices - - - - -	11
3 Placement of boxes and flux levels - - - - -	12
4 Decrease in beta with neutron bombardment - - - - -	13
5 Increase of I_{C0} with neutron bombardment - - - - -	14
6 Change of forward resistance with neutron bombardment, semiconductor diodes - - - - -	14
7 Change of back resistance with neutron bombardment, semiconductor diodes - - - - -	15
8 Changes in β parameters with neutron bombardment, total of twenty-four 2N139 transistors - - - - -	15
TABLES	
1 Average Values of Beta and I_{C0} after Irradiation - - - - -	17
2 Changes in Minority Carrier Lifetime and Beta with Neutron Bombardment - - - - -	18

SECRET

EFFECT of NUCLEAR RADIATION on SEMICONDUCTOR DEVICES

OBJECTIVES

The object of the work described herein was to ascertain the continued effects of neutron, gamma, and electromagnetic radiation upon commercially available transistors and diodes and upon electronic circuits employing these components. Particularly desired was specific information of value to the applications researcher as to the relative radiation susceptibility of the different types of semiconductor devices.

BACKGROUND

The use of nuclear weapons in modern warfare makes necessary the obtaining of information concerning the effects of nuclear radiation upon armaments and equipment. Since many of the armament control circuits either presently utilize semiconductor devices, or may advantageously do so, it is essential to obtain information on the performance of transistors and semiconductor diodes in the environment of a nuclear explosion.

Preliminary high-intensity, short-duration neutron-irradiation tests were made in 1956 (Reference 1) using the Los Alamos Scientific Laboratory's Godiva pulse reactor as a neutron source. The choice of semiconductor devices and the design of electronic circuitry exposed during Operation Plumblbob were made as indicated by the results of the Godiva test.

THEORY

Since the operation of semiconductor devices depends upon carrier movement through a well-ordered crystal lattice, it should be expected that particle bombardment of the crystal would disrupt its orderly arrangement and thereby cause device performance to deteriorate. In addition, the accompanying gamma rays were expected to cause ionization of matter (grease, potting compound, etc.) in contact with the crystal, resulting in surface effects detrimental to transistor action.

Decrease in the common-emitter forward current gain (β) of transistors as a result of continuous low-level neutron radiation over a long period of time has been measured by others (References 2 and 3). Since the loss of β has been attributed primarily to a decrease in minority carrier lifetime (References 3 and 4), it was expected that this would be of less proportional importance for high-frequency units, wherein the minority carriers diffuse through a thinner base region.

An increase in collector diode backward leakage current (I_{CO}) of irradiated transistors has also been measured by investigators using continuously operated reactors (References 2 and 3). This degradation has been attributed to a combination of surface effects at the collector-base junction, together with changes in bulk characteristics of the semiconductor that tend to destroy the barrier. The former effects, that of conductances shunting the collector-base barrier, have been considered to result (References 2 and 4) primarily from exposure to gamma radiation and are reported to vary considerably with the type of grease or filling compounds surrounding the

SECRET
RESTRICTED DATA

crystal, whereas the changes in both characteristics were attributed principally to neutron irradiation.

PROCEDURE

The semiconductor devices and circuits were exposed were placed between sponge rubber pads and contained in aluminum cans. The cans were packed in glass-wool insulation and placed inside heavy marine plywood boxes. The plywood boxes were buried at various distances from the ground-zero point of the nuclear detonation and at various depths in the ground in such a manner that exposure to neutron flux would vary from 10^7 to about 4×10^{11} total neutrons per square centimeter (NVT²), and gamma radiation from less than 1×10^4 to 50,000 r. Gold foils were included in each box to act as indicators of the relative intensity of neutron irradiation.

Figure 1 is a photograph of the containers for the transistors and devices exposed.

Semiconductor devices in both the passive and active states were exposed; however, monitor-



Figure 1. Containers for semiconductor devices for special tests.

ing was limited to before, instantaneous, and after recovery. Indicators were included on the trigger circuits to show if they had been activated.


Since the results of preliminary tests (Reference 1) indicated that low-frequency transistors were damaged less by neutron irradiation than were silicon transistor units, the majority of the transistors selected for test were of the former type.

Transistorized devices, depending upon irradiation, included the following information included: (1) sine-wave oscillators, which were driving item Number 1, (2) Class A amplifiers, (3) transistor trigger circuits, (4) types, and (5) photoelectric scanner-recorder, power supplies. Schematic circuit diagrams of the devices are shown in Figure 2.

In order to eliminate possible malfunctioning due to pickup from interconnecting cables, each sine-wave oscillator and trigger circuit was constructed on a common chassis, and the

²NVT is the product of the neutron flux and the exposure time in seconds (NVT = neutron/cm²/sec/sec).

The checking of the transistors' forward current gain (beta) and collector diode back leakage current (I_{CB}) was done with a laboratory-type beta checker. An ac-vacuum-tube voltmeter was used to monitor the outputs of the oscillators and amplifiers. The trigger circuits were self-monitoring by the use of small squibs, which ignited at a predetermined current level. Monitor-

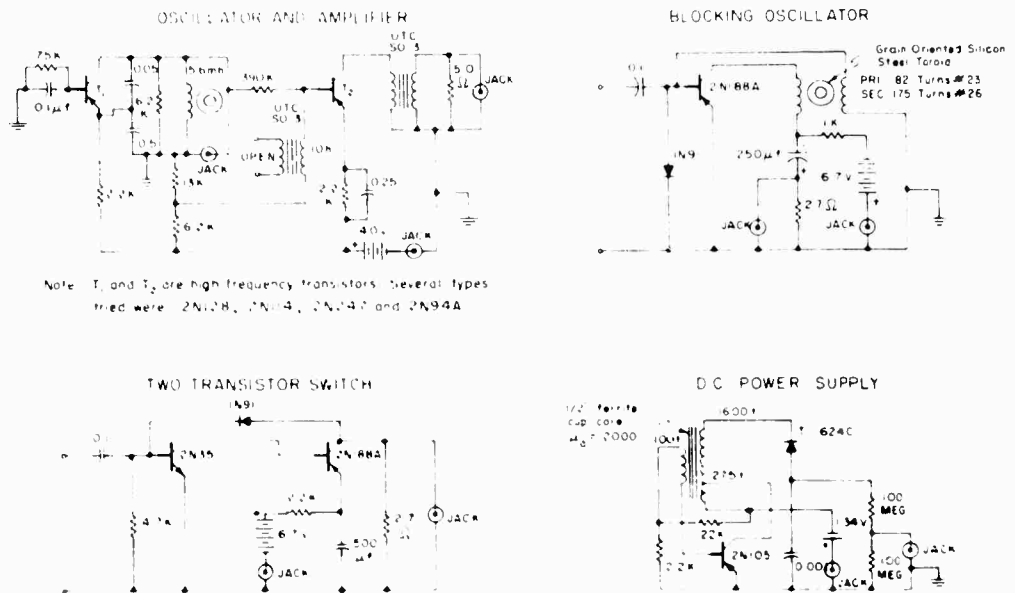

ing of the outputs of the dc-to-dc high-voltage power supplies was accomplished by using a high-impedance electrostatic voltmeter.

The measurements indicated above were taken and recorded before exposure to the radiation and were repeated again afterwards. In every case, after-exposure recovery of the equipment and its monitoring were accomplished before the self-contained batteries had run down enough to cause consequential error.

Data from several types of detectors, placed at various distances from ground zero as part of Project 2.3, provided a means for computing the total integrated neutron flux (NVT) levels. These values correlated well with relative values obtained from the gold-foil detectors placed inside the boxes.

A total of 293 transistors and 60 semiconductor diodes were irradiated in these tests; of these, 45 transistors were in the operating state during irradiation. Three samples each of representative types of commercially available transistors were exposed to the selected levels of nuclear radiation. A few of the less-available types were tested in smaller quantities.

Figure 3 shows the placement of the boxes containing the semiconductors and semiconductor devices relative to Shot Priscilla. The one box exposed to Shot Hood was buried 4 inches below the ground at 800 feet from ground zero.

The permanent performance capabilities of these particular transistorized devices were only slightly affected by exposure (under operating conditions) to atomic radiation up to 2.9×10^{12}

NVT and 3.3×10^3 r. As was experienced in the preliminary tests, component damage was manifest only in the semiconductor devices.

The oscillator and amplifier units, which utilized the same type of high-frequency transistors for both functions, showed negligible permanent effect from irradiation as intense as 10^{12} NVT and 150 r. A slightly higher exposure of 2.9×10^{12} NVT and 3.3×10^3 r resulted in percentage reductions in the amplifiers' outputs, by type of transistor used, as follows: 2N128, 3.0 percent; 2N114, 7.5 percent; 2N247, 15 percent; and 2N94A, 18 percent. The outputs of the oscillators remained practically unchanged after exposure at the above levels.

Trigger circuits of two types, blocking oscillators, and two transistor switches were exposed in the operative state with indicator squibs connected in the circuits to disclose false triggering. Although inspection of the circuits after recovery showed that no permanent damage to perform-

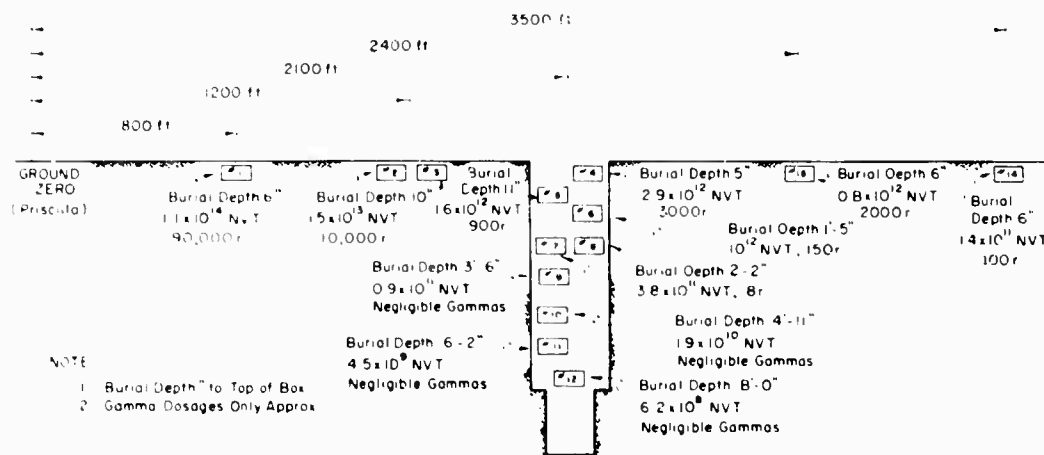


Figure 3 Placement of boxes and flux levels.

ance resulted from irradiation as high as 1.6×10^{12} NVT and 900 r, the expended indicator squibs showed that all circuits exposed to fluxes greater than 1.9×10^{10} NVT (with negligible gamma radiation) had been caused to trigger by the nuclear radiation. Two of the blocking oscillator circuits, which were more sensitive than the two-transistor trigger circuits, triggered from exposures of 4.5×10^7 and 6.2×10^7 NVT, respectively.

Subsequent checking showed that the batteries powering the two-transistor trigger circuits had run down considerably following the irradiation, whereas similar batteries powering the blocking oscillators remained at nearly original strength.

The results of irradiating the transistorized high-voltage power supplies were somewhat erratic. A unit exposed to 3.8×10^{11} NVT and 8 r suffered a 19 percent drop in output, whereas a similar one exposed to 1.6×10^{12} NVT and 900 r had its output decreased by only 2.4 percent (both four days after exposure).

The output of a unit irradiated at 0.9×10^{11} NVT and negligible gamma was not reduced. Laboratory testing of the supplies approximately 3 weeks after their irradiation showed that all the voltage outputs had recovered to within 2 percent of their pre-exposure values.

A check of semiconductor devices exposed to a nuclear detonation when in the passive state showed that most high-frequency transistors suffered moderate damage from exposure to fluxes of 1.1×10^{11} NVT (highest flux accurately instrumented) and 8.8×10^4 r. Exceptions to this were the surface-barrier transistors, the characteristics of which were only slightly altered by irradiation at this level. Of the several types of surface-barrier transistors tested, the 2N128 transistors exhibited the highest resistance to radiation damage. The average characteristics of three 2N128 transistors exposed to fluxes of 1.1×10^{11} NVT and 8.8×10^4 r indicated a loss in beta of less than 3.2 percent and an increase in I_{C0} of about 70 percent. (Highest I_{C0} was still

less than 2 μ at.) The change of characteristics of the 2N247 drift transistors from irradiation at the 1.1×10^{14} NVT level was somewhat unusual, since the average beta of the transistor dropped only about 30 percent, whereas the average I_{CO} increased to twelve times its pre-exposure level.

Results similar to those above were obtained when the same types of transistors were contained in a two-layer Boral (slow-neutron) shield container inside the regular aluminum housing, and this assembly was exposed to the same neutron and gamma-flux intensity.

Figures 4 and 5 show the decrease in forward current gain (beta) and the increase in reverse collector diode leakage current (I_{CO}), respectively, of several of the types of transistors passively exposed. Data showing the effects of radiation on the beta and I_{CO} of each of the transis-

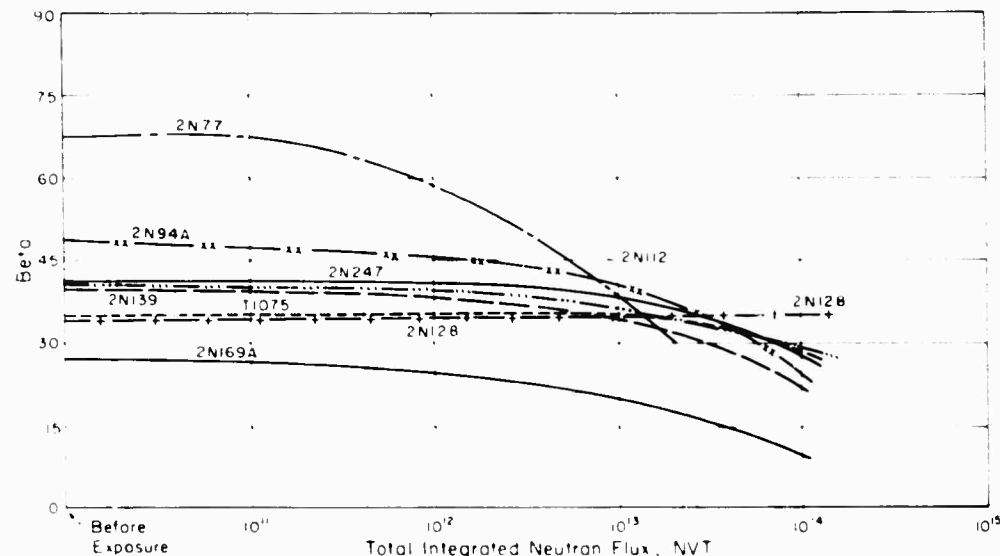


Figure 4 Decrease in beta with neutron bombardment.

tors passively exposed appears in Table 1. Both the graphs and the table show normalized values, i.e., the average original value altered by the average percent change. Where several transistors were exposed at a given flux level, the individual deviations from the average change were generally less than 30 percent. The transistors exposed while in operating condition in equipment were affected to approximately the same degree by irradiation as were the same type of passively exposed transistors.

Figures 6 and 7 show the increase in forward resistance and decrease in back resistance, respectively, of several types of semiconductor diodes included among the components passively exposed.

The changes in h parameters of the Type 2N139 transistors exposed to nuclear radiation when in the passive state are shown in Figure 8.

Table 2 lists the measured values of minority carrier lifetime and forward current gains for 2N77 transistors before and after exposure to several intensities of nuclear radiation.

DISCUSSION

It is believed that neutron bombardment was responsible for the permanent damage to the semiconductor devices exposed in these tests. Other investigators (References 2 and 3) have found that a gamma dosage of about 10^7 r was required to reach the threshold of permanent semiconductor damage. Since the maximum gamma dosage received by any component in these tests was less than 10^5 r, the possibility of permanent damages from gamma radiation is ruled out.

Although it was planned to irradiate the units of operating equipment at levels up to 2×10^{13} NVT, the maximum level to which operating units actually were exposed was 2.9×10^{12} NVT, a

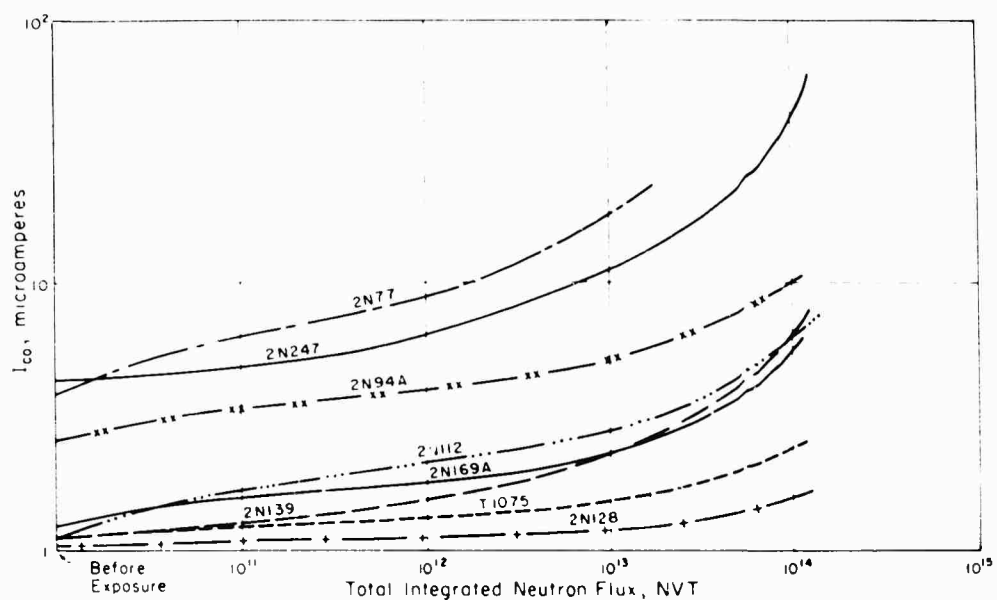


Figure 5 Increase of I_{CO} with neutron bombardment.

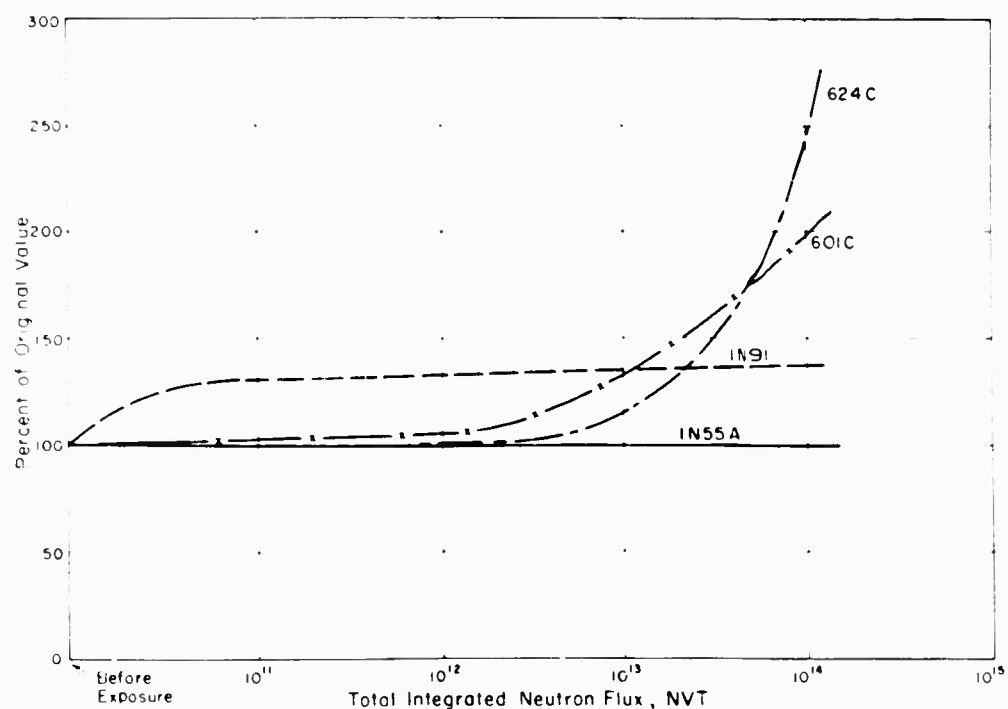


Figure 6 Change of forward resistance with neutron bombardment, semiconductor diodes.

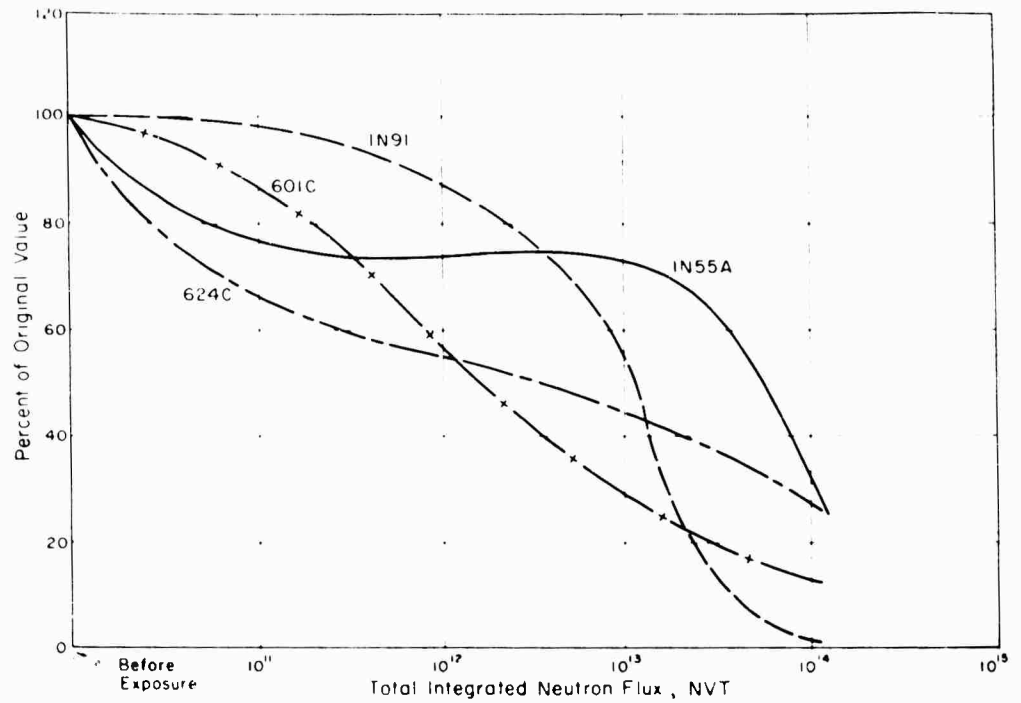


Figure 7 Change of back resistance with neutron bombardment, semiconductor diodes.

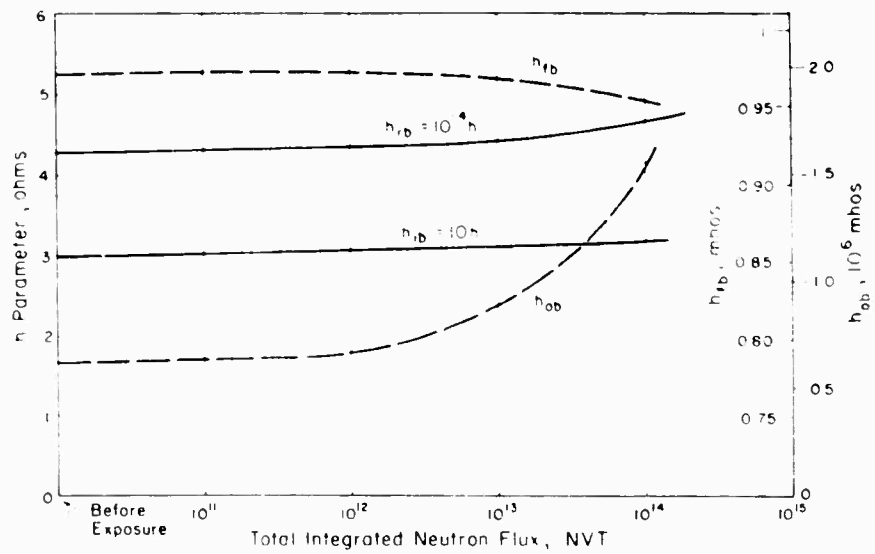


Figure 8 Changes in h parameters with neutron bombardment, total of twenty-four 2N139 transistors.

flux value less than expected at the selected exposure site and considerably below that to which the passive units were exposed.

It is to be expected that a neutron flux of 2.9×10^{12} NVT would only slightly affect the performance of transistorized devices using the high-frequency, thin-base, transistors. As occurred in the preliminary tests, the oscillator outputs were not affected, since the oscillators were designed with a relatively large amount of positive feedback and since the performance of the high-frequency transistors used as oscillators in this test deteriorated only slightly at exposures of 2.9×10^{12} NVT and below.

The reduction in output of the amplifiers, which occurred at the maximum exposure level (for active devices) of 2.9×10^{12} NVT, was almost directly proportional to the loss in forward current gain of the transistors. As was done in the preliminary tests, the amplifiers were purposely designed to reflect this deterioration. The maximum decrease in output of 18 percent (1.7 db), however, cannot be considered to constitute a device failure, for variances greater than this exist in commercially available transistors and are allowed for in conventional electronic design.

The false triggering of the blocking oscillator and two-transistor switch circuits is believed to be due to transient currents resulting from either the effects of neutron and gamma radiation on the semiconductor devices or the circuit intercepting the radiated electromagnetic field. The results indicate a triggering sensitivity to nuclear radiation of several orders of magnitude greater than that for permanent radiation damage to audio transistors.

The fact that the batteries powering the two-transistor switches ran down rapidly was attributed to the direct coupling employed from the collector of the NPN transistor to the base of the PNP transistor. The use of this type of coupling results in the I_{CO} of the NPN transistor being amplified by both transistors to cause a large collector current to flow in the PNP units. Since the I_{CO} of a transistor increases from irradiation, the disadvantage of using a direct coupled circuit is apparent.

The erratic behavior of the high-voltage power supplies may have been due to the combination of the spread of characteristics of the transistors and the fact that this particular design requires a transistor with high forward current gain and a high collector-base resistance at the instant of current cutoff.

Since only one supply was tested at each dosage level, anomalous behavior of the one sample (which would average out for many samples) could be responsible for the incongruous data. When laboratory tests were made, 3 weeks after the exposure, there had been sufficient annealing so that the direct-current output of the damaged unit was almost up to its original value.

The majority of transistors exposed to the nuclear radiation while in the passive state exhibited a decrease in beta and an increase in I_{CO} to approximately the same degree as was experienced for similar transistors in the preliminary tests. Since those contained in a Boral container were damaged to almost the same degree as were similar units not so contained, it appears that the elimination of low-energy neutrons causes no appreciable change in radiation damage.

The effects of the changes in h parameters on the performance of conventional transistor amplifiers should be considered. The power gain (P. G.) of a typical grounded emitter-transistor-amplifier stage is approximated by:

$$P. G. = (h_{fe})^2 \left(\frac{h_{oe}}{h_{oe} + R_L} \right) \frac{R_L}{h_{ie}} \quad (1)$$

Where: R_L the load resistance
h parameters per Institute of Radio Engineers' standards, corresponding to the hybrid parameters for a four-terminal network.

TABLE 1. AVERAGE VALUES OF β_{FA} AND I_{CB} AFTER IRRADIATION*

Transistor Type	Parameter	Before Exposure	Shot Peenalla									Shot Hood
			$1.1 \cdot 10^{14}$	$1.1 \cdot 10^{14}$	$1.5 \cdot 10^{15}$	$1.6 \cdot 10^{15}$	$3.8 \cdot 10^{15}$	$0.9 \cdot 10^{16}$	$0.8 \cdot 10^{16}$	$1.4 \cdot 10^{16}$	Approx $1 \cdot 10^{16}$	
2N77	β_{FA}	67.0			31.2	55.7	64.4		58.7	67.0	4.9	
Ge, audio, PNP	I_{CB}	3.9 μ A			± 5.5	± 3.0	± 4.7		2.7	± 1.7	± 4.2	
2N188A	β_{FA}	70.5	29.7		39.0			74.6	74.2	73.1		
Ge, audio, PNP	I_{CB}	7.1 μ A	± 7.8		± 2.6			± 1.4	± 1.8	± 1.4		
2N139	β_{FA}	39.3	18.6	22.6, 20.8	32.1, 31.6	37.2	38.4	37.9	38.5	37.9	11.9	
Ge, C, PNP	I_{CB}	1.1 μ A	± 6.8	± 6.6	± 2.7	± 1.5	± 1.3	± 1.3	± 1.6	± 1.4	± 11.1	
2N117	β_{FA}	40.2	28.5	18.8	33.7	38.4	39.9	40.2			8.0	
Ge, C, PNP	I_{CB}	1.1 μ A	± 6.0	± 6.4	± 2.6	± 2.0	± 1.7	± 1.6			± 1.3	
2N114	β_{FA}	73.1	47.8	63.0	76	74.6						
Ge, C, PNP	I_{CB}	1.0 μ A		± 4.0	± 2.2	± 1.1	± 1.3					
2N117	β_{FA}	41.4	36.1	28.2	35.6	41.4	39.7					
Ge, C, audio, PNP	I_{CB}	1.3 μ A	± 10.6	12.4	± 2.8	± 1.5	± 1					
2N148	β_{FA}	43.9	4.4	33.3	36.3	33.2					35.6	
Ge, C, S, PNP	I_{CB}	1.0 μ A		± 1.7	± 1.0	± 1.1	± 1.3				± 2.1	
110*	β_{FA}	4.4	27.3	26.9	33.2			33.7	33.6			
Ge, C, S, S, PNP	I_{CB}	1.1 μ A	± 1.9	± 1.0	± 1.5			± 1.4	± 1.6			
2N136	β_{FA}	27.6	21.0	25.3				26.8	26.3			
Ge, S, C, S, S, PNP	I_{CB}	1.3 μ A		± 2.1	± 1.1			± 1.0	± 1.5			
1.11 (1.11000)	β_{FA}	127	91.7	94.5	113	113					8	
Ge, S, S, C, S, PNP	I_{CB}	1.1 μ A	± 3.9	± 4.6	± 1.7	± 2.5					± 1.2	
1.1000	β_{FA}	10.6		6								
Ge, S, C, PNP	I_{CB}	0.76 μ A		± 1.03								
6A	β_{FA}	50.3	36.0	40.0								
Ge, S, C, PNP	I_{CB}	1.1 μ A		± 0.96	± 1.4							
1.1003	β_{FA}	200			81.2	171	206					
Ge, C, C, C, PNP	I_{CB}	1.1 μ A			± 2.0	± 1.0	± 1.0					
2N10	β_{FA}	8.6	10.2	18.7				21.3	27.2			
Ge, C, C, PNP	I_{CB}	0.4 μ A		± 7.6	± 1.0			± 3.4	± 1.9			
2N94	β_{FA}	4.2	13.6	21.7				34.7	34.2			
Ge, C, PNP	I_{CB}	1.0 μ A		± 6.4	± 1.9			± 6.0	± 2.3			
2N109A	β_{FA}	27.4	6	10.3	17.1			26.0	26.5			
Ge, C, PNP	I_{CB}	1.3 μ A	± 6.4	± 4.3	± 2.2			± 1.5	± 1.4			
2N94A	β_{FA}	48.4	20.7	14.2	37.1			48.5	45.0			
Ge, C, PNP	I_{CB}	1.3 μ A	± 1.1	± 1.9	± 1.9			± 1.3	± 1.8			
2N101	β_{FA}	109	70.3	103				118	114			
Ge, C, C, PNP	I_{CB}	1.7 μ A		± 4.0	± 1.1			± 3.1	± 2.5			
2K 700	β_{FA}	1.6			4.5	10.9						
Si, C, C, PNP	I_{CB}	0.3 μ A			± 1.5	± 1.0						
2N107	β_{FA}	34			46.4	54.0	54.8					
Si, C, PNP	I_{CB}	Not										
1.1100	β_{FA}	1			18.9	20.0						
Si, C, C, S, C, PNP	I_{CB}	1.1 μ A			± 1.0	± 1.0						
2N107	β_{FA}	93.0			87.2		95					
Ge, S, C, C, PNP	I_{CB}	1.3 μ A			± 1.0		± 1.0					
110X 100	β_{FA}	88			78.3	78.7						
Ge, S, C, C, PNP	I_{CB}	0.2 μ A			± 0.87	± 1.0						

* 1.1, 6, 10, 5A, 1

If one assumes that R_L is considerably smaller than h_{oe} , a condition met in most RC coupled transistor amplifiers and in many others, then the power gain equation reduces to:

$$P.G. = (h_{fe})^2 \frac{R_L}{h_{ie}} \quad (2)$$

Equation 2 indicates that the power gain of an amplifier stage is a function of the transistor parameters h_{ie} and h_{fe} ; however, the variance of the input impedance, h_{ie} , of a transistor from irradiation is relatively small in comparison to the change in h_{fe} , the forward current gain (beta). It follows that the power gain is approximately proportional to $(h_{fe})^2$. The extent of damage to an amplifier stage is thus seen to be a drop in power gain of about 6 db for each 50-percent decrease in beta of the transistor. Since 40 db of gain per transistor-amplifier stage is possible with high-gain transistors, a 6-db loss due to transistor damage might be tolerated in most cases. Variations of this relative magnitude could be reduced considerably by the application of negative

TABLE 2. CHANGES IN MINORITY CARRIER LIFE TIME AND BETA WITH NEUTRON BOMBARDMENT

Transistor Number	Time, μ sec		Beta		NVT Exposure
	Before	After	Before	After	
1	4.2	0.5 or less	61	4	10^{14}
2	5.7	*	79	5	10^{14}
3	3.2	*	67	3.2	10^{14}
4	4.6	2.7	74	36.5	1.5×10^{13}
5	4.4	3.5	46	22	1.5×10^{13}
6	5.0	2.5	57	25.5	1.5×10^{13}
7	4.4	3.1	57	47.5	1.6×10^{12}
8	8.3	3.5	78	66	1.6×10^{12}
9	4.9	5.5	93	76	1.6×10^{12}
10	4.5	4.8	60	54	3.8×10^{11}
11	8.5	5.6	76	76	3.8×10^{11}
12	8.3	2.1	57	56	3.8×10^{11}

* Value too low to measure.

feedback, and in addition, the negative feedback, if of the dc type, would increase the circuit stability. High circuit stability is particularly desirable for circuits exposed to nuclear radiation, because of the unavoidable increase in transistor I_{CO} .

The analysis above was made using the common-emitter transistor h parameters, since the majority of circuits now employ transistors using the common-emitter connection. Figure 8 shows radiation effects on the transistors' common base h parameters, the latter being used because they are the more commonly measured classical parameters. For either type of h parameter, the significant changes from irradiation are such as to cause similar performance degradations.

With the exception of a few anomalies, the measured minority carrier lifetimes listed in Table 2 are proportional to the loss of beta of the transistors. Of particular interest are Transistors 1, 2, and 3, which suffered an almost complete loss of beta and also showed extremely short minority carrier lifetimes.

CONCLUSIONS

Of the components normally used in electronic circuits, semiconductor devices are the most-susceptible to damage by nuclear radiation. In locations where physical survival of electronic equipment from the effects of a nuclear weapon is possible, fast-neutron bombardment alone is believed to be responsible for the permanent damage to semiconductor devices.

By designing circuits to be highly stable (using negative feedback and optimized biasing networks) and by using high-frequency transistors, the transistorized oscillators and amplifiers

of low-power type should still be usable after exposure to neutron fluxes as high as 10^{14} NVT. During the nuclear detonation, however, malfunctioning of certain electronic equipment employing semiconductor devices can be expected from exposures as low as 10^9 NVT, with negligible gamma radiation. It is yet to be determined whether either the neutron flux or the radiated electromagnetic field, or both, were responsible for malfunctioning during detonation.

Permanent damage to transistors from a nuclear detonation consists chiefly of a decrease in forward current gain, beta, and an increase in collector back leakage current, I_{CO} . Therefore, transistorized circuits subject to exposure to a nuclear detonation should be designed to be as self-compensating as possible for changes in these parameters. The designer should avoid circuits with outputs that are proportional to the forward current gain of the transistors.

High-frequency transistors were less susceptible to damage by fast-neutron irradiation than were the audio units. Surface-barrier units underwent an exposure of 1.1×10^{14} NVT from a detonation without suffering appreciable damage, whereas audio units were damaged severely by irradiation at this level. Of the surface-barrier transistors tested, Type 2N128 exhibited greatest resistance to radiation damage.

The irradiation of semiconductor diodes at levels up to 1.1×10^{14} NVT caused the back resistance of the diodes to decrease in all cases and, in most cases, caused the forward resistance to increase. The behavior of the germanium point-contact Type 1N55A was unusual, since its forward resistance remained fairly constant after irradiation.

The reasonable correlation in measured drop of minority carrier lifetime with loss of beta of irradiated transistors supports the theory that the decrease in beta is caused principally by the minority carrier lifetime decrease.

RECOMMENDATIONS

Tests should be made to ascertain and record semiconductor performance during exposure to a nuclear detonation and to ascertain specifically the degree of contribution to semiconductor malfunctioning of gamma, neutron, and electromagnetic field radiation during the explosion.

Functional transistor (and diode) circuitry should be constructed to be as radiation resistant as possible, and these circuits should be irradiated in operating condition to ascertain and record their performance both during and after exposure.

REFERENCES

1. W. V. Behrens and J. M. Shaul; "The Effects of Short Duration Neutron Radiation on Semiconductor Devices"; Proceedings of the Institute of Radio Engineers, Vol. 46, No. 3, March 1958; Unclassified.
2. J. C. Pigg and C. C. Robinson; "Effect of Radiation on Semiconductors"; Electrical Manufacturing, Vol. 59, No. 4, April 1957, Unclassified.
3. G. L. Keister and H. V. Stewart; "Preliminary Report of an Investigation of the Effects of Nuclear Radiation on Selected Transistors and Diodes", Contract AF-33 (038) 19589, Astia No. AD-123953; Unclassified.
4. D. B. Kret, "Analysis of Radiation Effects on Transistors"; Electronic Design, Vol. 5, No. 14, 15 July 1957; Unclassified.

DISTRIBUTION

Military Distribution Category 62

ARMY ACTIVITIES

- 1 Deputy Chief of Staff for Military Operations, D/A, Washington 25, D.C. ATTN: Dir. of DMAR
- 2 Chief of Research and Development, D/A, Washington 25, D.C. ATTN: Army Res.
- 3 Assistant Chief of Staff, Intelligence, D/A, Washington 25, D.C.
- 4 Chief of Staff, D/A, Washington 25, D.C. ATTN: ENGBB
- 5 Chief of Experimental Activities, D/A, Washington 25, D.C. ATTN: ENGBB
- 6 Chief of Staff, D/A, Washington 25, D.C. ATTN: ENGBB
- 7 Chief Signal Officer, D/A, Plans, Programs, and Insp. Div., Washington 25, D.C. ATTN: SIGINT
- 8 Commanding General, Chemical Warfare Command, Ft. Monmouth, N.J.
- 9 Director of Research and Development, Office, Headquarters, DARS, Ft. Bliss, Tex. ATTN: Capt. Chester L. Brown
- 10 President, U.S. Army Artillery Board, Ft. Hill, Okla.
- 11 President, U.S. Army Air Defense Board, Ft. Bliss, Tex.
- 12 President, U.S. Army Aviation Board, Ft. Rucker, Ala. ATTN: ATTN
- 13 Commander, U.S. Army Command & General Staff College, Ft. Leavenworth, Kansas. ATTN: ARCHIVE
- 14 Commander, U.S. Army Air Defense School, Ft. Bliss, Tex. ATTN: Command & Staff College
- 15 Commander, U.S. Army Artillery School, Ft. Monmouth, N.J.
- 16 Commander, U.S. Army Aviation School, Ft. Rucker, Ala.
- 17 Commander, U.S. Army Infantry School, Ft. Benning, Ga. ATTN: C.I.D.
- 18 Commanding General, Chemical Corps Training Center, Ft. McClellan, Ala.
- 19 Commander, USA Signal School, Ft. Monmouth, N.J.
- 20 Commanding Officer, Army Medical Research Lab., Ft. Kn x, Ky.
- 21 Commanding General, U.S. Army Chemical Corps Research and Development Center, Washington 25, D.C.
- 22 Commanding Officer, Chemical Warfare Lab., Army Chemical Center, Md. ATTN: Tech. Library
- 23 Commanding Officer, Chemical Warfare Lab., Washington 25, D.C. ATTN: Chem. Warfare Lab., Ft. Monmouth, N.J.
- 24 Commanding General, Aberdeen Proving Ground, Md. ATTN: Director, Ballistic Research Laboratory
- 25 Commanding General, U.S. Army Artillery School, Ft. Benning, Ala.
- 26 Commander, Army Rocket and Guided Missile Agency, Redstone Arsenal, Ala. ATTN: Tech. Library
- 27 Commanding General, White Sands Air Force Base, New Mexico, N. Mex. ATTN: RSG-M
- 28 Commander, Army Ballistic Missile Agency, Redstone Arsenal, Ala. ATTN: RSG-M
- 29 Commanding General, Ordnance Ammunition Center, J. Lee, Ill.
- 30 Commanding Officer, USA Signal R&D Laboratory, Ft. Monmouth, N.J.
- 31 Commanding General, U.S. Army Electronic Proving Ground, Ft. Belvoir, Ariz. ATTN: Tech. Library
- 32 Commanding General, USA Combat Surveillance Agency, 1134 N. Highland St., Arlington, Va.
- 33 Commanding Officer, USA Signal R&D Laboratory, Ft. Monmouth, N.J. ATTN: Tech. Div. Ctr., Evans Area
- 34 Director, Operations Research Office, Johns Hopkins University, 6333 Arlington Rd., Bethesda 14, Md.
- 35 Commander in Chief, U.S. Army Europe, APO 403, New York, N.Y. ATTN: Tech. Div., Weapons Br.

NAVY ACTIVITIES

- 41 Chief of Naval Operations, D/N, Washington 25, D.C. ATTN: OP-03EG
- 42 Chief of Naval Operations, D/N, Washington 25, D.C. ATTN: OP-75
- 43 Chief of Naval Operations, D/N, Washington 25, D.C. ATTN: OP-4.61
- 44 Chief of Naval Research, D/N, Washington 25, D.C. ATTN: Code 411
- 45 Chief, Bureau of Naval Weapons, D/N, Washington 25, D.C. ATTN: Code 411
- 46 Chief, Bureau of Ordnance, D/N, Washington 25, D.C. ATTN: Code 411
- 47 Chief, Bureau of Ships, D/N, Washington 25, D.C. ATTN: Code 411
- 48 Director, U.S. Naval Research Laboratory, Washington 25, D.C. ATTN: Mrs. Katherine E. Case
- 49 Commander, U.S. Naval Ordnance Laboratory, White Oak, Silver Spring 19, Md.
- 50 Commanding Officer and Director, Navy Electronics Laboratory, San Diego 32, Calif.
- 51 Commanding Officer, U.S. Naval Mine Defense Lab., Panama City, Fla.
- 52 Commanding Officer, U.S. Naval Radiological Defense Laboratory, San Francisco, Calif. ATTN: Tech. Info. Div.
- 53 Commanding Officer and Director, U.S. Naval Civil Engineering Laboratory, Fort Huachuca, Calif. ATTN: Code 411
- 54 Commanding Officer, U.S. Naval School Command, U.S. Naval Station, Treasure Island, San Francisco, Calif.
- 55 President, U.S. Naval War College, Newport, Rhode Island
- 56 Superintendent, U.S. Naval Postgraduate School, Monterey, Calif.
- 57 Commanding Officer, Air Development Squadron 5, VX-5, China Lake, Calif.
- 58 Commander, U.S. Marine Corps, Washington 25, D.C. ATTN: Code 411
- 59 Director, Marine Corps Landing Force, Development Center, MCR, Quantico, Va.
- 60 Commanding Officer, U.S. Naval CIC School, U.S. Naval Air Station, Myrtle Beach, S.C.
- 61 Chief of Naval Operations, Department of the Navy, Washington 25, D.C. ATTN: Code 411
- 62 Chief, Bureau of Naval Weapons, Navy Department, Washington 25, D.C. ATTN: Code 411

AIR FORCE ACTIVITIES

- 63 Hq. USAF, ATTN: Operations Analysis Office, Office, Vice Chief of Staff, Washington 25, D.C.
- 64 Air Force Intelligence Center, HQ. USAF, ACSI (AFM-71) Washington 25, D.C.
- 65 Director of Research and Development, DCS D. Hq. USAF, Washington 25, D.C. ATTN: Guidance and Weapons Div.
- 66 Commander, Theoretical Air Command, Langley AFB, Va. ATTN: Doc. Security Branch
- 67 Commander, Air Defense Command, Ent AFB, Colorado. ATTN: Assistant for Atomic Energy, ADEN-A
- 68 Commander, Air Research and Development Command, Andrews AFB, Washington 25, D.C. ATTN: RDRWA
- 69 Commander, Air Force Ballistic Missile Div. Hq. ARDC, Air Force Phil Post Office, Los Angeles 45, Calif. ATTN: WDSNT
- 70 Commander, AF Cambridge Research Center, 1111 Housem Field, Bedford, Mass. ATTN: CR-574

UNCLASSIFIED DATA

SECRET

- | | |
|---|---|
| <p>99-100 Commander, Air Force Special Weapons Center, Kirtland AFB, Albuquerque, N. Mex. ATTN: Tech. Info. & Intel. Div.</p> <p>100-101 Commander, 1st AF Aviator's Medicine, USAF, Aerospace Medical Center (AIC) Bldg. Air Force Base, Tex. ATTN: C-1, Corp. C-1, Bldg. 101</p> <p>100-102 Commander, 1st AF Sp. Wpn. Squadron, Bq. USAF, Washington 25, D.C.</p> <p>100-103 Commander, Wright Air Development Center, Wright-Patterson AFB, Dayton, Ohio. ATTN: WUACT (For WUACT)</p> <p>100-104 Director, USAF Project RAND, VIA: USAF Liaison Office, The RAND Corp., 1100 Main St., Santa Monica, Calif.</p> <p>100-105 Commander, Air Defense Systems Integration Div., L. C. Hunscom Field, Bedford, Mass. ATTN: SIBK-S</p> <p>100-106 Chief, Ballistic Missile Early Warning Project Office, 1100 Main St., Santa Monica, Calif. ATTN: C-1, Bldg. 101, Room 101</p> <p>100-107 Commander, Rome Air Development Center, AFRL, Griffiss AFB, N.Y. ATTN: Documents Library, RCGSL-1</p> <p>100-108 Commander, Air Technical Intelligence Center, USAF, Wright-Patterson AFB, Ohio. ATTN: APCIN-4R1a, Library</p> <p>100-109 Headquarters, 1st Missile Div., USAF, Vandenberg AFB, Calif. ATTN: General's Analysis Office</p> | <p>100-110 Chief, Defense Atomic Support Agency, Washington 25, D.C. ATTN: Document Library</p> <p>100-111 Commander, Field Command, DASA, Sandia Base, Albuquerque, N. Mex.</p> <p>100-112 Commander, Field Command, DASA, Sandia Base, Albuquerque, N. Mex. ATTN: PCIG</p> <p>100-113 Commander, Field Command, DASA, Sandia Base, Albuquerque, N. Mex. ATTN: PCWT</p> <p>100-114 Commander-in-Chief, Strategic Air Command, Offutt AFB, Neb. ATTN: OAMS</p> <p>100-115 U.S. Documents Officer, Office of the United States National Military Representative - 8 AF, APO 55, New York, N.Y.</p> |
|---|---|
- ATOMIC ENERGY COMMISSION ACTIVITIES
- | |
|---|
| <p>100-116 U.S. Atomic Energy Commission, Technical Library, Washington 25, D.C. ATTN: For DMA</p> <p>100-117 Los Alamos Scientific Laboratory, Report Library, P.O. Box 1606, Los Alamos, N. Mex. ATTN: Helen Redman</p> <p>100-118 Sandia Corporation, Classified Document Division, Sandia Base, Albuquerque, N. Mex. ATTN: H. C. Smyth, Jr.</p> <p>100-119 University of California Lawrence Radiation Laboratory, P.O. Box 808, Livermore, Calif. ATTN: David G. Craig</p> <p>100-120 Weapons Data Section, Office of Technical Information Extension, Oak Ridge, Tenn.</p> <p>100-121 Office of Technical Information Extension, Oak Ridge, Tenn. (Surplus)</p> |
|---|
- OTHER DEPARTMENT OF DEFENSE ACTIVITIES
- | |
|---|
| <p>100-122 Director of Defense Research and Engineering, Washington 25, D.C. ATTN: Tech. Library</p> <p>100-123 Director, Weapons Systems Evaluation Group, Room 1ER80, The Pentagon, Washington 25, D.C.</p> |
|---|

SECRET



Defense Special Weapons Agency
6801 Telegraph Road
Alexandria, Virginia 22310-3398

OPSSI

MAY 8 1998

MEMORANDUM FOR DISTRIBUTION

SUBJECT: Declassification Review of Operation PLUMBOB Test Reports

The following 101 reports concerning the atmospheric nuclear tests conducted during Operation PLUMBOB in 1957 have been declassified and cleared for open publication/public release:

WT-1401 thru WT-1409, WT-1417, WT-1419 thru WT-1424, WT-1424.1, WT-1425 thru WT-1438, WT-1440 thru WT-1444, WT-1447 thru WT-1455, WT-1457, WT-1459 thru WT-1462, WT-1464 thru WT-1470, WT-1472 thru WT-1477, WT-1480, WT-1482, WT-1484, WT-1485, WT-1487 thru WT-1490, WT-1492, WT-1493, WT-1495 thru WT-1502, WT-1504, WT-1505, WT-1507 thru WT-1509, WT-1511 thru WT-1513, WT-1519, WT-1522, WT-1525, WT-1527 thru WT-1532, WT-1534, WT-1535 and WT-1542.

An additional 13 WTs from PLUMBOB have been re-issued with deletions and are identified with an "EX" after the WT number. These reissued versions are unclassified and approved for open publication. They are:

WT-1410 thru WT-1416, WT-1418, WT-1445, WT-1471, WT-1517, WT-1521, and WT-1541.

This memorandum supersedes the Defense Special Weapons Agency, OPSSI memorandum same subject dated June 13, 1997 and may be cited as the authority to declassify copies of any of the reports listed in the first paragraph above.

RITA M. METRO
Chief, Information Security

DISTRIBUTION:
See Attached